

Current-driven dynamics of chiral ferromagnetic domain walls

Satoru Emori¹, Uwe Bauer¹, Sung-Min Ahn¹, Eduardo Martinez² and Geoffrey S. D. Beach^{1*}

In most ferromagnets the magnetization rotates from one domain to the next with no preferred handedness. However, broken inversion symmetry can lift the chiral degeneracy, leading to topologically rich spin textures such as spin spirals^{1,2} and skyrmions³⁻⁵ through the Dzyaloshinskii-Moriya interaction⁶ (DMI). Here we show that in ultrathin metallic ferromagnets sandwiched between a heavy metal and an oxide, the DMI stabilizes chiral domain walls^{2,7} (DWs) whose spin texture enables extremely efficient current-driven motion⁸⁻¹¹. We show that spin torque from the spin Hall effect¹²⁻¹⁵ drives DWs in opposite directions in Pt/CoFe/MgO and Ta/CoFe/MgO, which can be explained only if the DWs assume a Néel configuration^{7,16} with left-handed chirality. We directly confirm the DW chirality and rigidity by examining current-driven DW dynamics with magnetic fields applied perpendicular and parallel to the spin spiral. This work resolves the origin of controversial experimental results^{10,17,18} and highlights a new path towards interfacial design of spintronic devices.

Current-controlled DW displacement underpins the operation of an emerging class of spintronic memory¹⁹ and logic^{20,21} devices. In out-of-plane magnetized ferromagnets sandwiched between an oxide and a heavy metal, current-induced DW motion is anomalously efficient⁸⁻¹¹. This observation has been widely attributed to a Rashba effective field^{17,22,23} that stabilizes Bloch DWs against deformation, permitting high-speed motion¹⁰ through conventional spin-transfer torque²⁴ (STT). However, current-induced DW motion is absent in symmetric Pt/Co/Pt (refs 8,9, 11,25) stacks, and semiclassical transport calculations²⁵ suggest that the spin-polarized current in the ultrathin (<1 nm) Co is vanishingly small. Moreover, DWs in Pt/Co/oxide move against electron flow^{8,10,11}, contrary to the action of STT (ref. 24). Together, these results suggest that conventional STT contributes negligibly to DW dynamics in these ultrathin structures and that interfacial phenomena^{26,27} are instead responsible.

The Rashba field lacks the correct symmetry to drive DWs directly^{16,26,27}, and the spin Hall effect (SHE) in the adjacent heavy metal has emerged as a possible alternative mechanism^{12-16,27}. SHE-driven spin accumulation at the heavy-metal/ferromagnet interface generates a Slonczewski-like torque^{16,26,27} strong enough to switch uniformly magnetized films^{12-15,18}. However, the Bloch DWs expected in typical nanowire geometries^{8-11,28} have their plane oriented perpendicular to the nanowire axis, in which case the Slonczewski-like torque vanishes¹⁶. This behaviour was recently confirmed in asymmetric Pt/Co/Pt stacks in which the SHE-induced torques from the Pt layers did not cancel completely¹⁵. In that case, current-assisted DW depinning was observed when an applied field rotated the DW plane towards the

nanowire axis, but up-down and down-up DWs were driven in opposite directions and the current had no effect in the absence of the bias field. The SHE alone is therefore incapable of uniformly driving trains of DWs in devices, and is insufficient to explain the high spin-torque efficiencies and DW velocities observed in Pt/Co/oxide⁸⁻¹¹ without applied fields.

Here we characterize current-induced torques and DW dynamics in out-of-plane magnetized Pt/CoFe/MgO and Ta/CoFe/MgO stacks that are nominally identical except for the heavy-metal underlayers, whose spin Hall angles are large and of opposite sign¹²⁻¹⁴. By considering the symmetry of the measured current-induced torque along with the DW dynamics driven by this torque, we uniquely identify the DW configuration as Néel with a fixed chirality. Magnetostatics alone makes this configuration unstable and does not favour one chirality over the other, but the DMI has been theoretically shown to promote chiral Néel DWs (refs 2,7). By applying in-plane magnetic fields, we verify that the DW magnetization aligns rigidly along the nanowire axis, and that the DW spin spiral exhibits a global chirality common to both Pt/CoFe/MgO and Ta/CoFe/MgO. Current-driven DW motion in heavy-metal/ferromagnet/oxide structures is naturally explained by the combination of the SHE, which produces the sole current-induced torque, and the DMI, which stabilizes chiral DWs whose symmetry permits uniform motion with very high efficiency.

DW motion was characterized in 500-nm-wide, 40- μm -long nanowires overlaid with an orthogonal DW nucleation line and lateral contacts for current injection (Fig. 1a). We first examine the effect of current on the threshold field H_{prop} for DW propagation through the defect landscape. Measurements were performed as in ref. 11, by first nucleating a reversed domain with the Oersted field from a current pulse through the nucleation line and then sweeping an out-of-plane field H_z to drive the DW along the nanowire. DW motion was detected through the polar magneto-optical Kerr effect, with a $\approx 3 \mu\text{m}$ laser spot positioned at the midpoint of the nanowire. Comparing Fig. 1d,e, H_{prop} varies linearly with electron current density j_e , but DW propagation is hindered in the electron flow direction in Pt/CoFe/MgO and assisted along electron flow in Ta/CoFe/MgO. This remarkable difference, produced simply by changing the non-magnetic metal in contact with the ferromagnet, was independent of the sense of magnetization (up-down or down-up) across the DW. The magnitude of the spin-torque efficiency, taken as the slope of H_{prop} versus j_e , was 120 Oe per 10^{11} A m^{-2} for Pt/CoFe/MgO and 170 Oe per 10^{11} A m^{-2} for Ta/CoFe/MgO. These large efficiencies are comparable to those reported for Pt/Co/AlOx (refs 9,10) and Pt/Co/GdOx (ref. 11), suggesting that a universal mechanism governs current-driven DW motion in heavy-metal/ferromagnet/oxide.

¹Department of Materials Science and Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA, ²Dpto. Física Aplicada, Universidad de Salamanca, Plaza de los Caidos s/n E-38008, Salamanca, Spain. *e-mail: gbeach@mit.edu

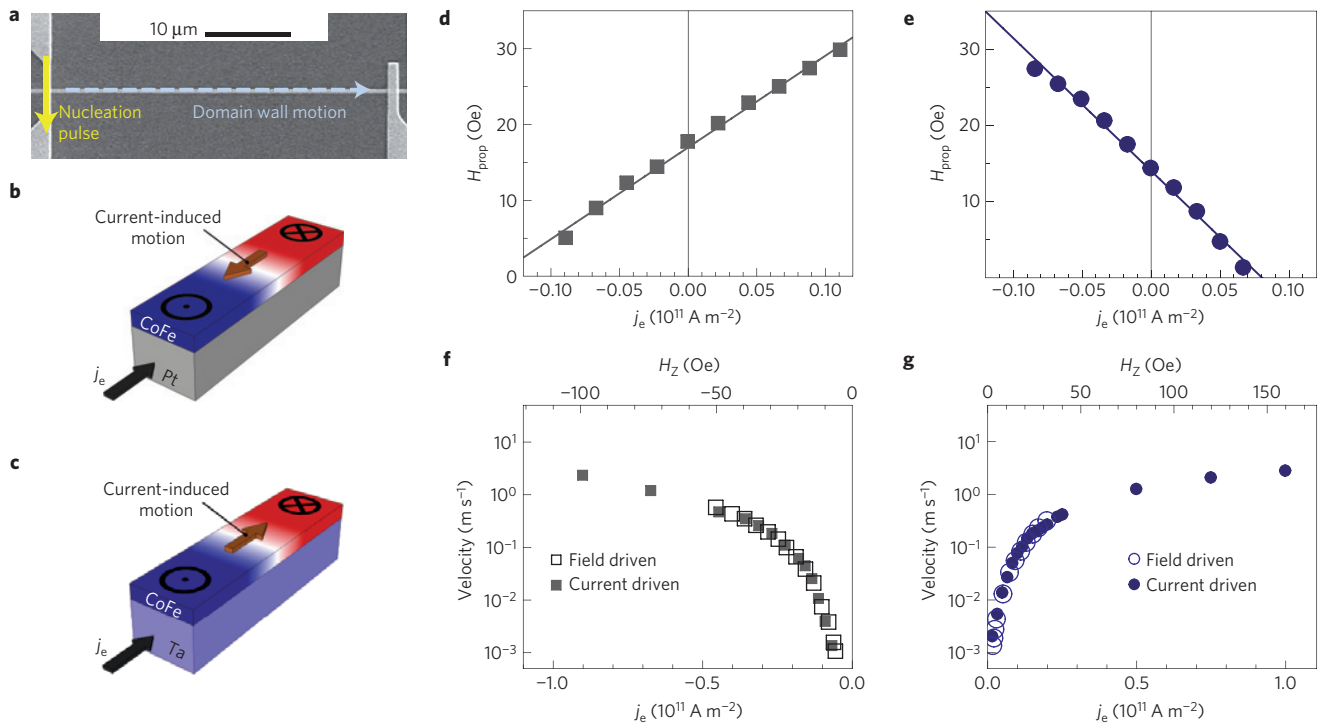


Figure 1 | Effect of current on DW motion. **a**, Scanning electron micrograph of the nanowire. The current pulse on the left nucleates a DW, which is then propagated to the right by current or applied out-of-plane field. **b,c**, Illustrations of the direction of current-driven DW motion in the Pt/CoFe/MgO (**b**) and Ta/CoFe/MgO (**c**) nanowires. Electron current j_e is defined positive when conduction electrons flow away from the nucleation line, from left to right in the micrograph (**a**). **d,e**, DW propagation field H_{prop} as a function of driving electron current density j_e for Pt/CoFe/MgO (**d**) and Ta/CoFe/MgO (**e**). The slope of the linear fit extracts the spin-torque efficiency for each structure. **f,g**, DW velocity as a function of j_e and applied out-of-plane field H_z for Pt/CoFe/MgO (**f**) and Ta/CoFe/MgO (**g**). The field-driven data are scaled by a field-to-current ratio (see text) so that they are directly on top of the current-driven data.

In Fig. 1f,g, we directly compare field-driven and current-driven DW velocities, measured using a time-of-flight technique¹¹. Again, DWs moved against electron flow in Pt/CoFe/MgO (Fig. 1f) and along electron flow in Ta/CoFe/MgO (Fig. 1g). The maximum field was limited by random domain nucleation, and the exponential dependence of velocity on H_z and j_e indicates thermally activated motion^{11,29}. The field-driven and current-driven velocities exhibit the same dynamical scaling across three decades in velocity when j_e is scaled by a constant (110 Oe per 10^{11} A m^{-2} for Pt/CoFe/MgO and 160 Oe per 10^{11} A m^{-2} for Ta/CoFe/MgO). These field-to-current ratios closely match those extracted from Fig. 1d,e. We therefore conclude that the effect of current on DW motion is phenomenologically equivalent to an out-of-plane field^{9,11}, which reveals the symmetry of the current-induced torque as discussed later.

In addition to robust DW motion, current enables switching between uniformly magnetized up and down states with the assistance of a constant in-plane magnetic field^{12,15,18}. This switching phenomenon was demonstrated in 1,200-nm-wide Hall crosses (Fig. 2a). A sequence of 250-ms-long current pulses with increasing (or decreasing) amplitude was injected along the x axis, and in between each pulse the out-of-plane magnetization component M_z was measured from the anomalous Hall voltage using a low-amplitude ($\sim 10^9 \text{ A m}^{-2}$) a.c. sense current and a lock-in amplifier. Figure 2d,e plots M_z versus j_e , under a constant applied longitudinal field H_L . This field tilted the magnetization away from the z axis by $\approx 5^\circ$ in Pt/CoFe/MgO at 500 Oe and $\approx 3^\circ$ in Ta/CoFe/MgO at 100 Oe, but did not bias M_z up or down, as evidenced by the nearly symmetric switching profile (Fig. 2d,e). With sufficiently large H_L and j_e in the $+x$ direction, the up magnetized state was favoured in Pt/CoFe/MgO (Fig. 2d, solid line), whereas the down state was favoured in Ta/CoFe/MgO (Fig. 2e, solid line). When the direction

of H_L or j_e was reversed, the preferred magnetization direction was also reversed (Fig. 2d,e, dotted lines).

This switching behaviour implies that j_e generates an effective field \mathbf{H}_{SL} associated with a Slonczewski-like torque^{12,13,15,18}, given by $\mathbf{H}_{\text{SL}} = H_{\text{SL}}^0 (\hat{m} \times (\hat{z} \times \hat{j}_e))$ (ref. 16). Here \hat{m} , \hat{z} and \hat{j}_e are unit vectors along the magnetization, z axis and electron flow, respectively, and H_{SL}^0 parameterizes the torque. The SHE in the heavy metal directly generates a Slonczewski-like torque, but the Rashba effect can also yield a torque of this form due to spin relaxation^{18,26,27}. Assuming the SHE is the dominant source, justified experimentally below, H_{SL}^0 is related to the spin Hall angle θ_{SH} in the heavy metal through $H_{\text{SL}}^0 = \hbar \theta_{\text{SH}} |j_e| / (2|e|M_S t_F)$ (ref. 16), with M_S being the saturation magnetization and t_F the ferromagnet thickness. From the sign of H_{SL}^0 extracted from current-induced switching (Fig. 2b,c), θ_{SH} is positive in Pt and negative in Ta, consistent with refs 12,13.

We quantified the Slonczewski-like torque by detecting magnetization tilting induced by a.c. current using the anomalous Hall voltage as described in refs 22,30 (see Supplementary Information). The scaling of H_{SL} with current is shown in Fig. 3. When the magnetization was up and j_e was in the $+x$ direction, H_{SL} pointed along $-x$ in Pt/CoFe/MgO (Fig. 3a,e) and $+x$ in Ta/CoFe/MgO (Fig. 3b,f), in agreement with our analysis of magnetization switching (Fig. 2b,c). The direction of H_{SL} reversed when the magnetization was oriented down. The linear fit in Fig. 3a reveals a large H_{SL}^0 in Pt/CoFe/MgO of magnitude 50 Oe per 10^{11} A m^{-2} , implying $\theta_{\text{SH}} = +0.06$ in Pt, which agrees well with ref. 12. The magnitude of H_{SL}^0 in Ta/CoFe/MgO is $\approx 200 \text{ Oe per } 10^{11} \text{ A m}^{-2}$, implying $\theta_{\text{SH}} = -0.25$ in Ta, twice as large as in ref. 13 and closer to the value reported for W (ref. 14).

The current-induced effective transverse field H_{FL} , often associated with a field-like torque from the Rashba effect^{16,17,22,23,26,27}, was quantified similarly^{22,30} (see Supplementary Information). Unlike H_{SL} , the direction of H_{FL} was independent of the magnetization

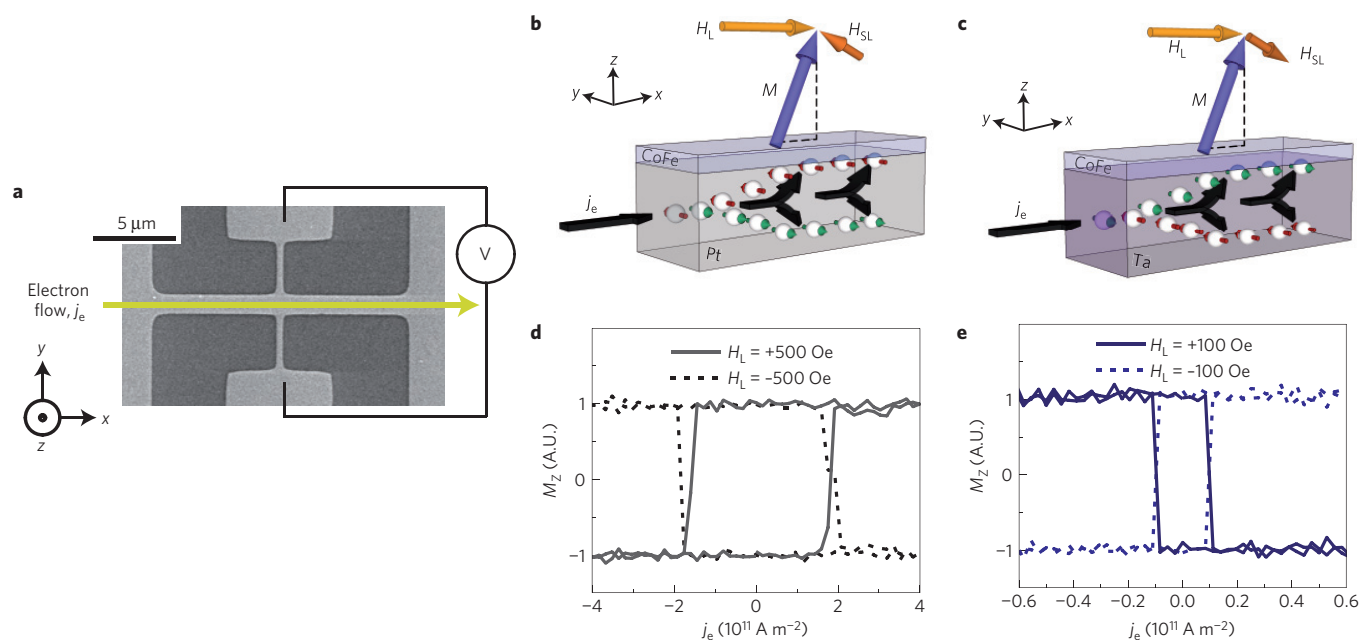


Figure 2 | Current-induced switching under a constant in-plane longitudinal field. **a**, Scanning electron micrograph of a Hall cross. **b,c**, Illustrations of Pt/CoFe/MgO (**b**) and Ta/CoFe/MgO (**c**) in the up magnetization state with the injected electron current and applied longitudinal field H_L in the $+x$ direction. Owing to the combination of the current-induced Slonczewski-like torque (producing an effective field H_{SL}) and the applied longitudinal field, up magnetization is stable in Pt/CoFe/MgO whereas it is unstable in Ta/CoFe/MgO. **d,e**, Out-of-plane magnetization M_z (normalized anomalous Hall signal) as a function of electron current density j_e under a constant H_L in Pt/CoFe/MgO (**d**) and Ta/CoFe/MgO (**e**). The magnitude of H_L is 500 Oe for Pt/CoFe/MgO (**d**) and 100 Oe for Ta/CoFe/MgO (**e**). When H_L is reversed from $+x$ (solid line) to $-x$ (dotted line), the stable magnetization direction under a given current polarity reverses.

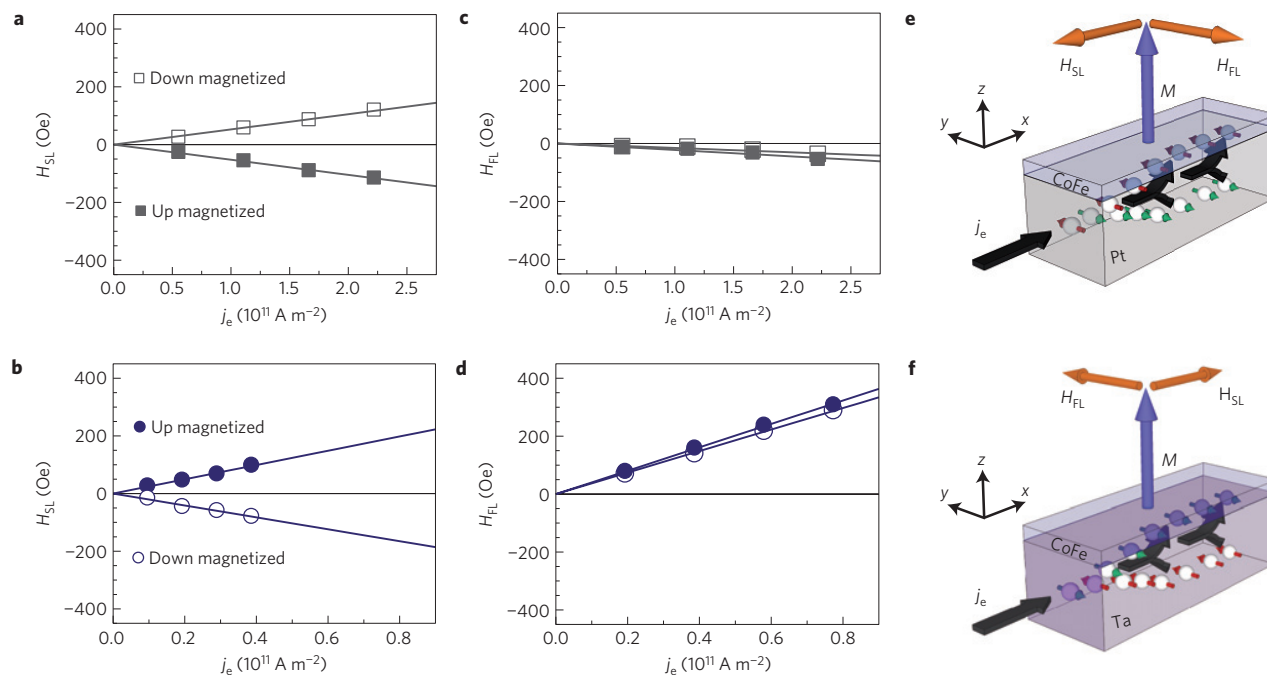


Figure 3 | Current-induced effective fields. **a,b**, Current-induced effective longitudinal field H_{SL} , arising directly from the Slonczewski-like torque, as a function of electron current density j_e (from a.c. excitation current amplitude) in Pt/CoFe/MgO (**a**) and Ta/CoFe/MgO (**b**). **c,d**, Current-induced effective transverse field H_{FL} as a function of j_e in Pt/CoFe/MgO (**c**) and Ta/CoFe/MgO (**d**). **e,f**, Illustration of the directions of the current-induced effective fields H_{SL} and H_{FL} in Pt/CoFe/MgO (**e**) and Ta/CoFe/MgO (**f**), when the magnetization is up and the electron flow is in the $+x$ direction.

orientation (Fig. 3c,d). The magnitude of H_{FL} in Pt/CoFe/MgO (Fig. 3c) was ≈ 20 Oe per 10^{11} A m^{-2} , two orders of magnitude lower than reported in refs 17,22, although its directionality was the same

as in Pt/Co/AlOx (refs 17,22). As current-induced DW motion had a very high efficiency and occurred against the electron flow direction in Pt/CoFe/MgO, the fact that H_{FL} was negligible indicates

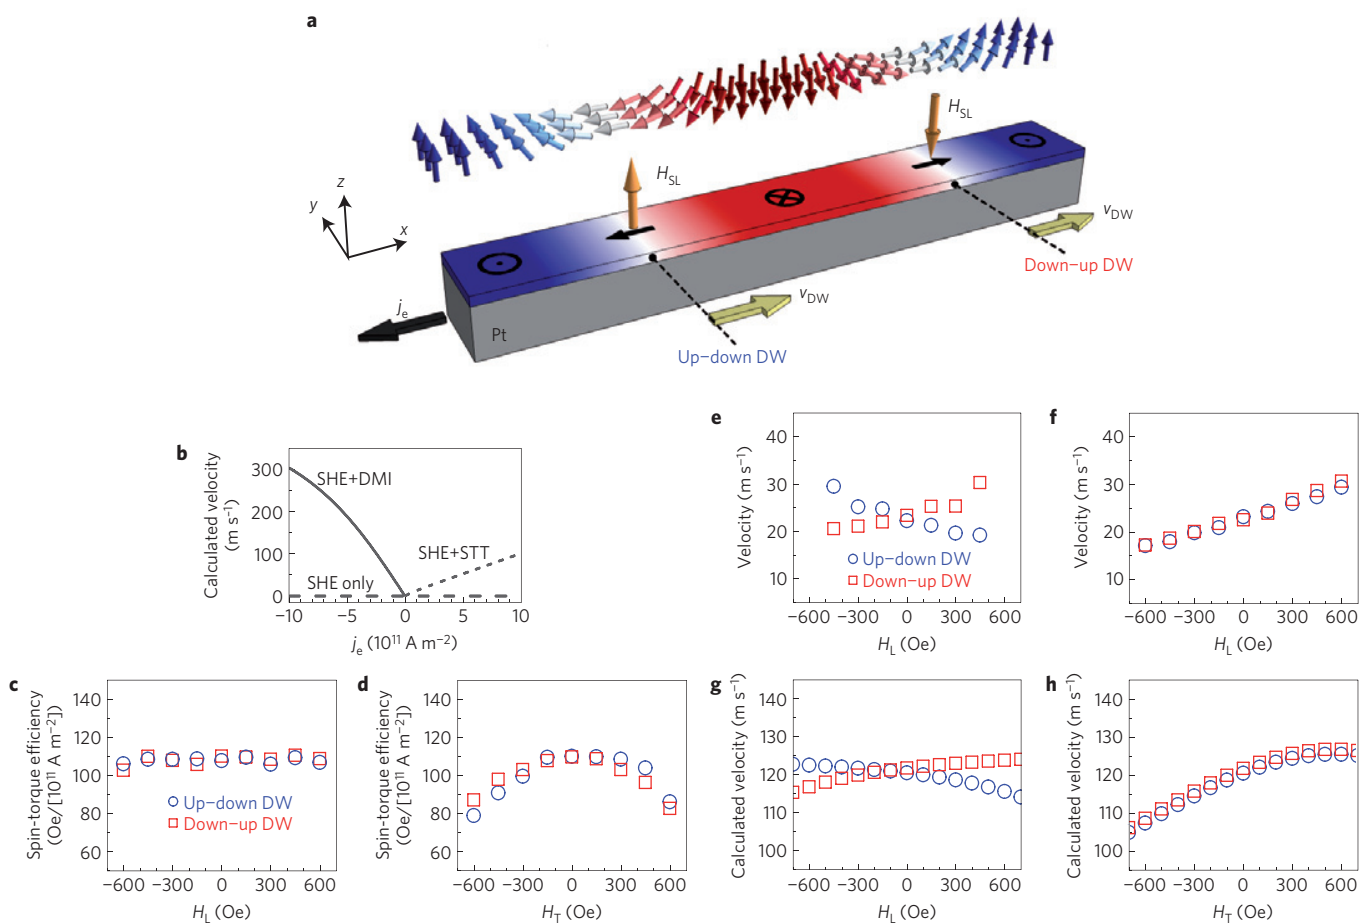


Figure 4 | Current-driven dynamics of chiral Néel DWs. **a**, Illustration of left-handed chiral Néel DWs in Pt/CoFe/MgO. The effective field H_{SL} from the Slonczewski-like torque moves adjacent up-down and down-up domains with velocity v_{DW} in the same direction against electron flow j_e . **b**, DW velocity as a function of electron current density j_e , calculated using the 1D model, with the SHE alone, the SHE and STT (SHE+STT), and the SHE and the DMI (SHE+DMI). The parameters used in this calculation are in the Methods. **c,d**, Spin-torque efficiency for DW motion in Pt/CoFe/MgO under applied longitudinal field H_L (**c**) and transverse field H_T (**d**). **e,f**, DW velocity at a constant current $j_e = -3.0 \times 10^{11} \text{ A m}^{-2}$ as a function of H_L (**e**) and H_T (**f**). **g,h**, Calculated DW velocity at $j_e = -3.0 \times 10^{11} \text{ A m}^{-2}$ as a function of H_L (**g**) and H_T (**h**) using the 1D model.

that the Rashba effect cannot be the source of these features^{8–11,26,27}. Furthermore, as any contribution to the Slonczewski-like torque by the Rashba effect¹⁸ enters as a correction proportional to the non-adiabicity parameter $\beta < 1$ (refs 26,27), the fact that H_{SL} is here much larger than H_{FL} implies that the Rashba effect contributes negligibly to the Slonczewski-like torque.

In Ta/CoFe/MgO (Fig. 3d), H_{FL} was in contrast quite large, $\approx 400 \text{ Oe}$ per 10^{11} A m^{-2} , and its direction was the same as in Ta/CoFeB/MgO (ref. 23) and opposite to Pt/CoFe/MgO and Pt/Co/AlOx (refs 17,22). This result suggests that in addition to the Slonczewski-like torque, a strong Rashba field^{17,22,23} may exist in this sample. However, the origin of the measured H_{FL} is beyond the scope of the present discussion and will require further investigation.

As summarized in Fig. 3e,f, the current-induced torques are opposite in Pt/CoFe/MgO and Ta/CoFe/MgO, as are the direction of current-driven DW motion and the sign of the spin Hall angles in Pt and Ta. Here we consider in detail the case of Pt/CoFe/MgO, in which the field-like torque is unambiguously small. One-dimensional (1D) model calculations²⁹ in Fig. 4b (see Methods and Supplementary Information) show that Bloch DWs cannot be driven by the SHE alone, in agreement with previous reports^{16,27} and with the symmetry of the Slonczewski-like torque. In the 1D model with $\theta_{SH} > 0$ and with no transverse Rashba field, the addition of conventional STT enables sustained DW motion,

but its direction is along electron flow (Fig. 4b). No combination of the SHE and STT reproduces the experimentally observed DW motion against electron flow (Supplementary Information), and moreover conventional STT is probably absent as argued above. Thus, an alternative mechanism is required whereby the SHE alone can drive DW motion.

Néel DWs have an internal magnetization that would align with the nanowire axis, such that the Slonczewski-like torque would manifest as a z -axis field¹⁶ as experimentally observed (Fig. 1). However, the direction of H_{SL} depends of the sense of the DW magnetization, and the direction of DW motion varies accordingly (Supplementary Information). Figure 4a illustrates Néel DWs with oppositely directed internal magnetization for up-down and down-up transitions, exhibiting a left-handed chiral texture². On the basis of the sign of the measured Slonczewski-like torque (Figs 2 and 3), these chiral DWs move against electron flow in Pt/CoFe/MgO and along electron flow in Ta/CoFe/MgO. Although Bloch DWs are magnetostatically preferred²⁸, adding the DMI to the 1D model stabilizes such chiral Néel DWs (ref. 7; Methods and Supplementary Information), leading to qualitative behaviour in agreement with experiment (Fig. 4b).

Finally, we assess the rigidity and chirality of the Néel DWs in Pt/CoFe/MgO using applied in-plane fields. In Fig. 4c,d we show that the spin-torque efficiency, extracted similarly to Fig. 1d, is insensitive to H_L up to at least 600 Oe, but declines significantly

